

Photoemission Evidence for Valence Fluctuations and Kondo Resonance in YbAl_2

Masaharu MATSUNAMI^{1,2*}, Ashish CHAINANI², Munetaka TAGUCHI², Ritsuko EGUCHI^{2†}, Yasutaka TAKATA², Masaki OURA², Makina YABASHI², Kenji TAMASAKU², Yoshinori NISHINO^{2‡}, Tetsuya ISHIKAWA², Masashi KOSAKA³, and Shik SHIN^{1,2,4}

¹*Institute for Solid State Physics, University of Tokyo, Kashiwa, Chiba 277-8581, Japan*

²*RIKEN SPring-8 Center, Sayo-cho, Sayo-gun, Hyogo 679-5148, Japan*

³*Graduate School of Science and Engineering, Saitama University, Saitama 338-8570, Japan*

⁴*Japan Science and Technology Agency (JST), Core Research for Evolutional Science and Technology (CREST), Chiyoda-ku, Tokyo 102-0075, Japan*

We use hard x-ray photoemission spectroscopy (HAXPES) to investigate the electronic structure of YbAl_2 , for which the Yb valence has not been consistently reported to date. The bulk sensitivity and the analytical simplicity provided by the Yb 3d core-level HAXPES allow a reliable determination of the mean valence of Yb ions. For YbAl_2 , it is evaluated to be +2.20, which remains nearly unchanged below 300 K. The Kondo resonance peak with an extremely high Kondo temperature (above 2000 K) is clearly identified in the valence-band spectra. The results indicate that a coherent Kondo state can be robust even in a nearly divalent system.

KEYWORDS: YbAl_2 , valence fluctuation, photoemission spectroscopy, HAXPES

For a long time, rare-earth intermetallic compounds have attracted much attention, since they exhibit a wide variety of strongly correlated electronic phenomena associated with the valence instability of these rare-earth ions.^{1,2} Recently, the concept of valence fluctuations has received renewed interest in relation to the unconventional quantum critical phenomena, particularly for Yb-based compounds such as YbRh_2Si_2 ³ or $\beta\text{-YbAlB}_4$.⁴ Theoretically, the role of the critical valence fluctuations has been invoked to explain their properties.⁵ The importance of critical valence fluctuations provides us with an opportunity to reexamine the valence fluctuation phenomena. Experimentally, the most fundamental issue is to precisely determine the mean valence, which is a measure of the f -electron occupation and localization.

Hard x-ray photoemission spectroscopy (HAXPES) with an excitation energy of 5–8 keV is one of the best-suited techniques. Apart the well-known bulk sensitivity, HAXPES can probe the Yb 3d core levels, located at a binding energy (E_B) of 1500–1600 eV, which is usually not possible with laboratory sources. For the Yb 3d core-level spectra, the divalent ($4f^{14}$, fully occupied) and the trivalent ($4f^{13}$, one-hole localized) features are well separated, thus allowing highly reliable valence determination. Indeed, HAXPES has been applied to various Yb-based compounds, such as the valence transition system YbInCu_4 ,^{6–8} the valence fluctuation systems YbAl_3 ,^{7,9} and YbCu_2Si_2 ,^{7,10} the divalent systems Yb metal and YbS ,¹⁰ the Kondo semiconductor YbB_{12} ,¹¹ and the heavy-fermion superconductor YbAlB_4 .¹² In this

letter, we demonstrate a precise determination of the Yb valence for YbAl_2 , which has also been considered as a prototypical valence fluctuation system.

YbAl_2 crystallizes in the cubic Laves MgCu_2 structure. The electrical resistivity shows a normal metallic behavior without a coherence peak in the temperature (T) range below 300 K.^{13–16} The electronic specific-heat coefficient, which provides a measure of effective electron mass, exhibits a slightly enhanced value, $\sim 10\text{--}17\text{ mJ/K}^2\text{mol}$.^{14–16} The magnetic susceptibility has a broad maximum (T_{max}) at 800–850 K and is nearly independent of T below 300 K after subtracting the impurity contribution.^{13,15,17,18} The Kondo T (T_K) has been estimated as 2000–2600 K from the $3T_{\text{max}}$ or the inelastic neutron scattering.¹⁹ The Yb valence has been investigated by some techniques such as the lattice parameters^{17,20} and the x-ray absorption spectroscopy (XAS) at the Yb- L_{III} edge.^{20–22} In addition, the valence-band photoemission spectroscopy (PES) using $h\nu = 70$,²³ 1487 (Al- $K\alpha$),²⁴ and 1254 eV (Mg- $K\alpha$)²⁵ has also been applied to study Yb valence. The reported valence values, however, have considerably large variation between +2.0 and +2.6. Such a large discrepancy may be caused by surface effects,²⁶ surface oxidation, or inconsistent precision of analysis. After carefully overcoming such considerations, our HAXPES results provide a conclusive Yb mean valence and consistency with its estimated T_K . Furthermore, the Kondo resonance peak is identified in the valence-band spectra, indicating that a coherent Kondo ground state can be robust even in a nearly divalent system such as YbAl_2 .

The single crystals of YbAl_2 were grown by the lithium flux method.¹⁶ Clean sample surfaces were obtained by fracturing *in situ*. Synchrotron-based HAXPES experiments were carried out at the undulator beamline BL29XUL in SPring-8, using $h\nu = 7940\text{ eV}$ and a hemi-

*E-mail: matunami@ims.ac.jp; Present address: UVSOR Facility, Institute for Molecular Science, Okazaki 444-8585, Japan

†Present address: Graduate School of Natural Science and Technology, Okayama University, Okayama 700-8530, Japan

‡Present address: Research Institute for Electronic Science, Hokkaido University, Sapporo 060-0812, Japan

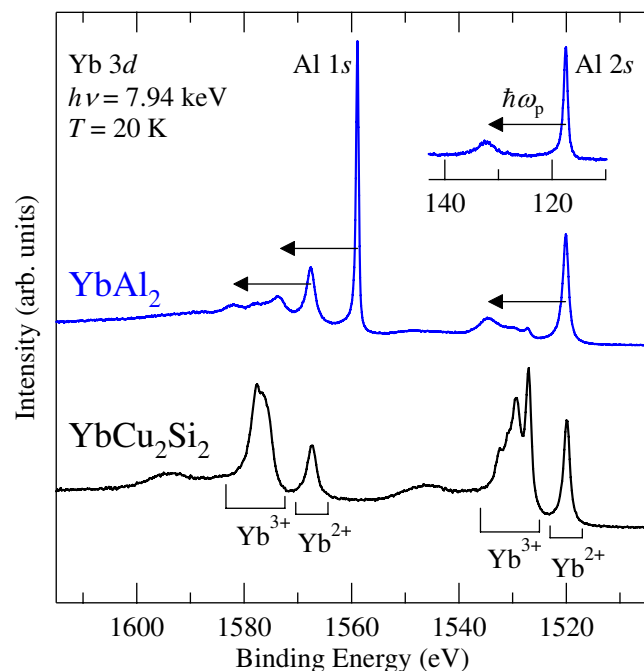


Fig. 1. (Color online) Yb $3d$ core-level HAXPES spectrum including the Al $1s$ core level for YbAl₂ in comparison with that for YbCu₂Si₂.¹⁰ Inset shows the Al $2s$ core-level spectrum, which is plotted with the same energy scale as the main panel, with the satellite due to plasmon excitations. Arrows represent the plasmon energy $\hbar\omega_p = 14.32$ eV.

spherical electron analyzer, Scienta R4000-10 kV.²⁷ The total energy resolution was set to 250 and 170 meV for the measurements of the core-level and valence-band spectra, respectively. To obtain the higher-resolution (50 meV) valence-band spectrum, we also performed soft x-ray (SX-) PES at the undulator beamline BL17SU using $h\nu = 580$ eV and Scienta SES-2002.²⁸ The E_B of samples was calibrated using the Fermi level (E_F) of an evaporated Au film.

Figure 1 shows the Yb $3d$ core-level spectrum of YbAl₂ at 20 K, compared with that of YbCu₂Si₂, which is known to show a Yb valence of +2.8.¹⁰ The sharp peak at $E_B = 1559$ eV is due to the Al $1s$ core level. The Yb $3d$ core-level spectra are separated into the $3d_{5/2}$ region at 1515–1540 eV and the $3d_{3/2}$ region at 1560–1585 eV owing to spin-orbit splitting. Both the spin-orbit components in YbCu₂Si₂ show two final-state configurations: the $3d^9 4f^{14}$ (Yb²⁺) line at ~ 1520 and ~ 1568 eV, and the $3d^9 4f^{13}$ (Yb³⁺) multiplets at ~ 1525 – 1538 and ~ 1572 – 1583 eV, which are due to the valence fluctuations. Similarly for YbAl₂, a clear Yb²⁺ line and weak Yb³⁺ multiplets can be observed, although we also find the Al $1s$ core level positioned between $3d_{5/2}$ and $3d_{3/2}$ regions and overlapped satellite features. The satellite features are caused by the energy loss due to plasmon excitations ($\hbar\omega_p = 14.32$ eV), as confirmed by measuring the Al $2s$ core-level spectrum shown in the inset of Fig. 1.

In order to determine the Yb mean valence for YbAl₂, the obtained spectra were analyzed in terms of the atomic multiplet model for free Yb²⁺ and Yb³⁺ ions.²⁹

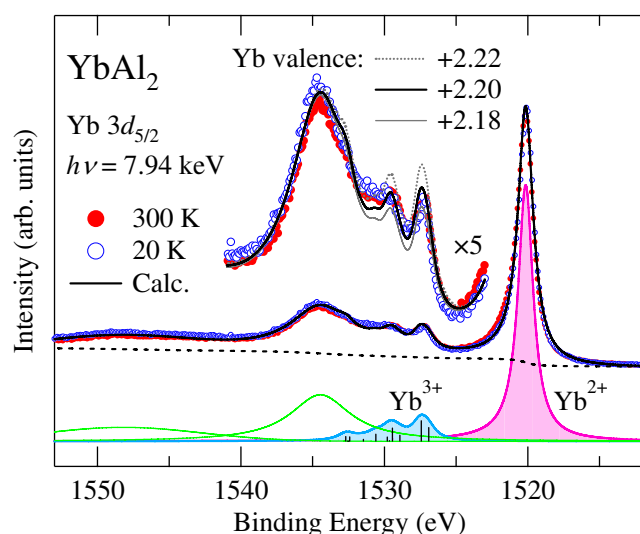


Fig. 2. (Color online) Comparison of the experimental spectra with the calculation by the atomic-multiplet model for the Yb $3d_{5/2}$ core level including the energy-loss satellites. The atomic multiplets are broadened in both terms of lifetime and experimental resolution. Dashed curve represents the integral background. In the expanded panel, the calculated reference spectra with Yb valence of $+2.20 \pm 0.02$ are also plotted.

Figure 2 shows the Yb $3d_{5/2}$ core-level spectra at 300 and 20 K, in comparison with those obtained from the atomic-multiplet calculation. The calculated discrete spectra were broadened by a Doniach-Šunjić function convoluted with a Gaussian representing the experimental energy resolution. The energy-loss satellites were fitted with a Lorentzian for the relatively intense peak at ~ 1534 eV and a Gaussian for the broad peak at ~ 1548 eV. As a background, the standard integral type one was used. The experimental spectra for both T are well reproduced by the calculation with the Yb mean valence of +2.20, which is obtained from the weight ratio between Yb²⁺ and Yb³⁺ components. As can be confirmed in the expanded panel in Fig. 2, the experimental spectra are located well between the calculated reference spectra, and hence, the accuracy in determining the Yb mean valence is estimated as $\sim \pm 0.02$.

Figure 3 shows the T -dependent Yb valence in YbAl₂ evaluated from the lattice parameters,^{17,20} the XAS at the L_{III} edge,^{20–22} the valence-band PES,^{23–25} and the above-described HAXPES. In the following, we discuss the origin of the large discrepancy among the results of these techniques. Since the lattice parameters as well as the magnetic susceptibility probe an average signal of Yb²⁺ and Yb³⁺ components, it is intrinsically difficult to estimate a precise Yb valence. This difficulty may be related to the large variation among two results for YbAl₂.^{17,20} On the other hand, using spectroscopies such as XAS and PES, each component can be separately probed. The Yb L_{III} -edge XAS is a well-known powerful tool for investigating the electronic structure, including the Yb-valence determination, and can be performed even under magnetic field and/or external pressure. However, Yb²⁺ and Yb³⁺ components in spectra are rela-

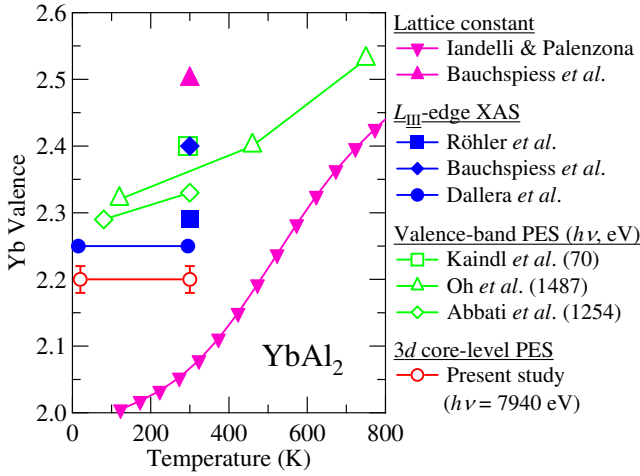


Fig. 3. (Color online) T dependence of Yb valence in YbAl_2 evaluated from the lattice parameters,^{17,20} the XAS at L_{III} edge,^{20–22} the valence-band PES,^{23–25} and the 3d core-level HAXPES in the present study.

tively broad and overlap significantly with each other, thus limiting the reliability of Yb valence determination compared with the Yb 3d core-level PES. Moreover, in the case of powder samples, as are used in XAS studies under high pressure,^{20,22} surface oxidation effects can have a serious impact on the Yb valence even with the bulk sensitive probe. Such a problem has been pointed out in terms of an extra trivalent signal derived from the surface Yb_2O_3 layer in the HAXPES of a purely divalent system, YbS.¹⁰ For YbAl_2 , the sharp rise at low T in the magnetic susceptibility has also been attributed to the surface Yb_2O_3 as an impurity.^{13,15,18} In our HAXPES measurements using *in-situ*-fractured single crystals of YbAl_2 , no O-1s signal has been detected. Therefore, the major difference in estimating Yb valence using XAS and our HAXPES results can be due to the surface oxidation of powder samples in XAS. Next, the HAXPES results are compared with previous lower photon energy valence-band PES studies.^{23–25} Since the valence-band spectra must include signals from orbitals other than Yb 4f electrons spread over a wide energy, it is difficult to precisely estimate the Yb valence, compared with the core-level spectroscopies. In the case of the low-energy PES, more importantly, the surface $\text{Yb}^{2+}\text{-}4f$ components can be observed, thus making it very difficult to obtain the precise bulk valence. For the previous PES with $h\nu=70\text{ eV}$,²³ such components might be overestimated, leading to a larger value of bulk valence than the intrinsic value. Subsequent SX-PES studies with $h\nu=1487$ ²⁴ and 1254 eV ²⁵ also assumed extra surface $\text{Yb}^{2+}\text{-}4f$ components, which could not be separated with the bulk ones because of the limited resolution, and hence also estimated a relatively large bulk valence. Actually, even in SX-PES with lower-energy $h\nu=580\text{ eV}$ for YbAl_2 , the surface $\text{Yb}^{2+}\text{-}4f$ components are negligibly small, as shown later. As a result, the simplicity of the experimental data and its analysis for bulk sensitive Yb 3d core-level HAXPES provides a high reliability in Yb valence determination.

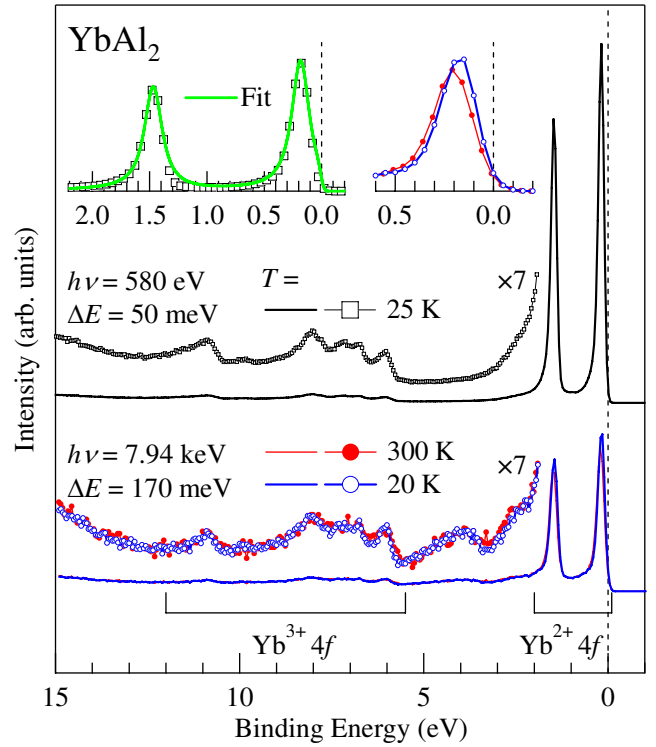


Fig. 4. (Color online) T dependence of valence-band HAXPES spectra and the high-resolution SX-PES spectrum at 25 K of YbAl_2 . Left inset shows the fitting result of the $\text{Yb}^{2+}\text{-}4f$ doublet in the SX-PES spectrum. Right inset shows the expanded scale of the HAXPES spectra in the near- E_F region.

The T independence of the Yb valence below 300 K is a distinct behavior compared with the other valence fluctuation systems such as YbAl_3 ^{7,9} and YbCu_2Si_2 .⁷ It can be understood in terms of the extremely high T_K ($=2000\text{--}2600\text{ K}$) in YbAl_2 , since the valence should vary significantly around T_K . This finding is consistent with the electrical resistivity showing no coherence peak^{13–16} and the constant magnetic susceptibility below 300 K.^{13,15,17}

We now discuss the electronic structure of YbAl_2 on the basis of the valence-band spectra, which also reflects the fluctuating Yb valence.³⁰ Figure 4 shows the T -dependent valence-band HAXPES spectra and the high-resolution SX-PES spectrum at 25 K, which are normalized for integrated intensity up to $E_B=13\text{ eV}$. The most prominent features are two sharp peaks between $E_F\text{--}2\text{ eV}$, which are derived from the $\text{Yb}^{2+}\text{-}4f$ doublet ($J=7/2$ and $5/2$) corresponding to the $4f^{13}$ final state. Next, two weak structures are observed at $2\text{--}5\text{ eV}$ in the HAXPES spectra, but not in the SX-PES spectrum. According to the band calculation³¹ and taking into account the photoionization cross sections,³² these can be attributed to Al 3s and 3p states. The multiple peak feature observed at $5\text{--}12\text{ eV}$ is due to the $\text{Yb}^{3+}\text{-}4f$ multiplet corresponding to the $4f^{12}$ final state. The existence of a fractional Yb^{3+} component is consistent with the fact that YbAl_2 is not a purely divalent system. It is important to note that the $\text{Yb}^{2+}\text{-}4f_{7/2}$ peak crosses E_F , in contrast to the case of purely divalent Yb systems in which this peak is located significantly below E_F .¹⁰

In order to analyze this peak, the $\text{Yb}^{2+}\text{-}4f$ doublet in the SX-PES spectrum was fitted by two Doniach-Šunjić functions multiplied with a Fermi-Dirac distribution at $T=25\text{K}$ and convoluted with a Gaussian, as shown in the left inset of Fig. 4. The spectrum is reproduced well by this simple fitting, which does not include any background and/or surface components. The obtained position and the intrinsic width (FWHM) of the $4f_{7/2}$ peak are 180 and 170 meV, respectively, both of which are in excellent agreement with the estimated T_K ($=2000\text{--}2600\text{K}$) and, in particular, the characteristic peak position ($=180\text{meV}$) in inelastic neutron scattering.¹⁹ Therefore, the $\text{Yb}^{2+}\text{-}4f_{7/2}$ peak can be identified as the Kondo resonance peak, thereby providing conclusive evidence for Kondo screening in YbAl_2 and consistency with the T_{max} behavior in the magnetic susceptibility.^{13,18} This finding establishes that the coherent Kondo ground state can be robust even in a nearly divalent regime.

Although the T dependence is small in the valence-band spectra as well as the core-level spectra, the $\text{Yb}^{2+}\text{-}4f$ peaks slightly shift by $\sim 30\text{meV}$ toward lower E_B with cooling, as shown in the right inset of Fig. 4, in contrast to the unshifted behavior of the $\text{Yb}^{3+}\text{-}4f$ multiplet. Such T variation has also been observed in YbAl_3 , and it was suggested to be a signature of the deviation from the framework of the single-impurity Anderson model.⁹ In addition, the weight of the Yb^{2+} component slightly increases with cooling, suggesting a slight reduction of Yb valence within the error bar.³⁰ It is noted that since the Kondo effect is intrinsically associated with the hybridization between conduction band and f -electron states and since the estimated T_K of YbAl_2 is very high, it is expectedly difficult to estimate the small change in T -dependent hybridization between 20 and 300 K.

In conclusion, we performed HAXPES and SX-PES on YbAl_2 . From the $\text{Yb}3d$ core-level spectra, the mean valence of Yb ions was evaluated to be $+2.20$, which remained nearly unchanged below 300 K. Through the comparison with those obtained by other techniques, the reliability of the valence determined by HAXPES was demonstrated. Furthermore, the Kondo resonance peak was identified in the valence-band spectra, indicating that a coherent Kondo ground state can be robust even in a nearly divalent system such as YbAl_2 .

Acknowledgment We thank H. Okamura and S. Kimura for valuable comments. The measurements of HAXPES and SX-PES were carried out with the approval of the RIKEN SPring-8 Center (Proposals No. 20090041 and No. 20090033, respectively). This research is supported by the Japan Society for the Promotion of Science (JSPS) through its Funding Program for World-Leading Innovative R&D on Science and Technology (FIRST) Program.

Nature Phys. **4** (2008) 603.

- 1) C. M. Varma: Rev. Mod. Phys. **48** (1976) 219.
- 2) J. M. Lawrence, P. S. Riseborough, and R. D. Parks: Rep. Prog. Phys. **44** (1981) 1.
- 3) O. Trovarelli, C. Geibel, S. Mederle, C. Langhammer, F. M. Grosche, P. Gegenwart, M. Lang, G. Sparn, and F. Steglich: Phys. Rev. Lett. **85** (2000) 626.
- 4) S. Nakatsuji, K. Kuga, Y. Machida, T. Tayama, T. Sakakibara, Y. Karaki, H. Ishimoto, S. Yonezawa, Y. Maeno, E. Pearson, G. G. Lonzarish, L. Balicas, H. Lee, and Z. Fisk:

- 5) S. Watanabe and K. Miyake: Phys. Rev. Lett. **105** (2010) 186403.
- 6) H. Sato, K. Shimada, M. Arita, K. Hiraoka, K. Kojima, Y. Takeda, K. Yoshikawa, M. Sawada, M. Nakatake, H. Namatame, M. Taniguchi, Y. Takata, E. Ikenaga, S. Shin, K. Kobayashi, K. Tamasaku, Y. Nishino, D. Miwa, M. Yabashi, and T. Ishikawa: Phys. Rev. Lett. **93** (2004) 246404.
- 7) L. Moreschini, C. Dallera, J. J. Joyce, J. L. Sarrao, E. D. Bauer, V. Fritsch, S. Bobev, E. Carpena, S. Huotari, G. Vankó, G. Monaco, P. Lacovig, G. Panaccione, A. Fondacaro, G. Paolicelli, P. Torelli, and M. Grioni: Phys. Rev. B **75** (2007) 035113.
- 8) S. Suga, A. Sekiyama, S. Imada, J. Yamaguchi, A. Shigemoto, A. Irizawa, K. Yoshimura, M. Yabashi, K. Tamasaku, A. Higashiya, and T. Ishikawa: J. Phys. Soc. Jpn. **78** (2009) 074704.
- 9) S. Suga, A. Sekiyama, S. Imada, A. Shigemoto, A. Yamasaki, M. Tsunekawa, C. Dallera, L. Braicovich, T.-L. Lee, O. Sakai, T. Ebihara and Y. Ōnuki: J. Phys. Soc. Jpn. **74** (2005) 2880.
- 10) M. Matsunami, A. Chainani, M. Taguchi, R. Eguchi, Y. Ishida, Y. Takata, H. Okamura, T. Nanba, M. Yabashi, K. Tamasaku, Y. Nishino, T. Ishikawa, Y. Senba, H. Ohashi, N. Tsujii, A. Ochiai, and S. Shin: Phys. Rev. B **78** (2008) 195118.
- 11) J. Yamaguchi, A. Sekiyama, S. Imada, H. Fujiwara, M. Yano, T. Miyamachi, G. Funabashi, M. Obara, A. Higashiya, K. Tamasaku, M. Yabashi, T. Ishikawa, F. Iga, T. Takabatake, and S. Suga: Phys. Rev. B **79** (2009) 125121.
- 12) M. Okawa, M. Matsunami, K. Ishizaka, R. Eguchi, M. Taguchi, A. Chainani, Y. Takata, M. Yabashi, K. Tamasaku, Y. Nishino, T. Ishikawa, K. Kuga, N. Horie, S. Nakatsuji, and S. Shin: Phys. Rev. Lett. **104** (2010) 247201.
- 13) E. E. Havinga, K. H. J. Buschow, and H. J. van Daal: Solid State Commun. **13** (1973) 621.
- 14) N. Tsujii, K. Yoshimura, and K. Kosuge: J. Phys.: Condens. Matter **15** (2003) 1993.
- 15) T. Görlach, C. Pfeleiderer, K. Grube, and H. v. Löhneysen: Phys. Rev. B **71** (2005) 033101.
- 16) H. Nowatari, Y. Saiga, Y. Kato, K. Iwata, S. Katano, T. Fujiwara, Y. Uwatoko, and M. Kosaka: J. Phys. Soc. Jpn. **76** (2007) Suppl. A, 80.
- 17) A. Iandelli and A. Palenzona: J. Less-Common Met. **29** (1972) 293.
- 18) J. C. P. Klaasse, J. W. E. Sterkenburg, A. H. M. Bleyendaal, and F. R. de Boer: Solid State Commun. **12** (1973) 561.
- 19) A. P. Murani, A. D. Taylor, R. Osborn, and Z. A. Bowden: Philos. Mag. B **65** (1992) 1333.
- 20) K. R. Bauchspeiss, W. Boksche, E. Holland-Moritz, H. Launois, R. Pott, and D. Wohlleben: in *Valence Fluctuations in Solids*, ed. L. M. Falicov, W. Hanke, and M. B. Maple (North-Holland, Amsterdam, 1981).
- 21) J. Röhlér, G. Krill, J.-P. Kappler, M.-F. Ravet, and D. Wohlleben: in *Valence Instabilities*, ed. P. Wachter and H. Boppert (North-Holland, Amsterdam, 1982).
- 22) C. Dallera, E. Annese, J.-P. Rueff, A. Palenzona, G. Vankó, L. Braicovich, A. Shukla, and M. Grioni: Phys. Rev. B **68** (2003) 245114.
- 23) G. Kaindl, B. Reihl, D. E. Eastman, R. A. Pollak, N. Märtensson, B. Barbara, T. Penney, and T. S. Plaskett: Solid State Commun. **41** (1982) 157.
- 24) S.-J. Oh, J. W. Allen, B. Barbara, T. Penney, and T. S. Plaskett: J. Magn. Magn. Mater. **52** (1985) 183.
- 25) I. Abbati, B. DeMichelis, A. Fasana, M. Sancrotti, A. Iandelli, G. L. Olcese, and R. Eggenhöfner: Solid State Commun. **65** (1988) 743.
- 26) The probing depth in low-energy (VUV-SX) PES, HAXPES, and L_{III} -edge (fluorescence-yield) XAS is generally considered as <20 and $\sim 80\text{Å}$, and $\sim 10\mu\text{m}$, respectively.
- 27) T. Ishikawa, K. Tamasaku, and M. Yabashi: Nucl. Instrum. Methods Phys. Res., Sect. A **547** (2005) 42; Y. Takata, M. Yabashi, K. Tamasaku, Y. Nishino, D. Miwa, T. Ishikawa,

- E. Ikenaga, K. Horiba, S. Shin, M. Arita, K. Shimada, H. Namatame, M. Taniguchi, H. Nohira, T. Hattori, S. Södergren, B. Wannberg, and K. Kobayashi: Nucl. Instrum. Methods Phys. Res., Sect. A **547** (2005) 50.
- 28) K. Horiba, R. Eguchi, N. Kamakura, K. Yamamoto, M. Matsunami, Y. Takata, Y. Senba, H. Ohashi, and S. Shin: AIP Conf. Proc. **879** (2007) 1611.
- 29) The details of the calculations are shown in R. Cowan: *The Theory of Atomic Structure and Spectra* (University of California Press, Berkeley, CA, 1981). The Slater integrals $F^k(4f, 4f)$, $F^k(3d, 4f)$, and $G^k(3d, 4f)$ were scaled to 80, 93, and 81 %, respectively.
- 30) The Yb mean valence estimated from the valence-band spectra in Fig. 4 is $+2.30 \pm 0.05$ (20 K) and $+2.31 \pm 0.05$ (300 K) for HAXPES and $+2.13 \pm 0.03$ (25 K) for SX-PES. The discrepancy with the valence estimated with Yb $3d$ core-level HAXPES can be attributed to the existence of orbitals other than Yb $4f$ electrons spread over a wide energy, which cannot be accurately separated, in valence-band spectra.
- 31) S. J. Lee, S. Y. Hong, I. R. Fisher, P. C. Canfield, B. N. Harmon, and D. W. Lynch: Phys. Rev. B **61** (2000) 10076.
- 32) J. J. Yeh and I. Lindau: At. Data Nucl. Data Tables **32** (1985) 1.